

## PRODUCT NOTES

This semi-toughened epoxy prepreg system was specifically formulated for better oven cure processing than the 2510 general aviation (AGATE) prepreg system. 2511 provides excellent all-around structural properties with a high wet and dry TG while offering a flexible cure temperature (250°F to 350°F, 121°C to 177°C) with a very low void content. This prepreg system also can be used in industrial and recreational applications.



### Industry Material Specification

Material procurable to CMA specification TCPF-T-2511 or Aerospace Material Specification (AMS) 3962.



### Easy Layup

Product allows complex part layup with minimal cuts or ridge lines. It maintains a comparable class A finish through post-cure, minimizing sanding and finishing times.



### Readily Available

AMS products, marked with this icon, are kept in stock and ready to ship.



### Industry Database

Select products listed in CMH-17 Vol 2. Contact us for more information.



### Flexible Cure Methods

Curing methods include autoclave or oven cure. Product can be cured with or without using a dwell.



### High Heat Tolerance

High Tg is suitable for structures exposed to elevated service temperatures.

## AVAILABLE PRODUCT FORMATS

2511 resin is available with numerous types of unidirectional carbon fibers and woven and glass fabrics with Fiber Areal Weight (FAW) ranging from 70 g/m<sup>2</sup> to 300 g/m<sup>2</sup> and Resin Content, (RC%) by weight percent, ranging from 24% to 44%. The table below lists commonly available product formats. Unidirectional products can be slit to widths between 1/8" and 60", and fabric products to widths above 6". Common product formats include: 1/4", 1/2", 1", and 1.5" AFP spools (UD only); 6", 500mm, 9", and 12" ATL rolls; and 24" to full width rolls for hand layup.

PART NUMBER	FIBER FORMAT	FIBER TYPE/STYLE	FAW (GSM)	RC % WEIGHT	ROLL WIDTH
P711AG-15	Unidirectional	T700G-12K-31E	150	35	39
F6273C-11M (AMS 3962)	Plain Weave	T700S-12K-50C	190	42	38
P211AS-200	Unidirectional	T800SC-24K-10E	200	35	60
FM6673G-11M	Plain Weave	T830HB-6K-41B	195	42	60
P6111-200	Unidirectional	M46JB-12K-50C	200	38	39
F4289-11M	Plain Weave	M46JB-6K-50C	202	42	39
FGF108-11M	Plain Weave	Style 108 E-Glass	48	42	38


## STORAGE LIFE

Out Life	28 days @ 75 °F (24 °C)
Freezer Life	24 months @ <10 °F (-12 °C)

## NEAT RESIN PHYSICAL PROPERTIES

PROPERTY	METHOD	UNITS	VALUE
Density	ASTM D792	g/cc	1.267
Tg (Dry)	ASTM D7028	°F (°C)	324 (162)
Tg (Wet)	ASTM D7028	°F (°C)	244 (118)
$K_{IC}$	ASTM D5045	ksi*in <sup>0.5</sup>	0.75
Minimum Viscosity	ASTM D4440	Poise	70.8
		°F (°C)	218 (103)

## RESIN VISCOSITY CURVE

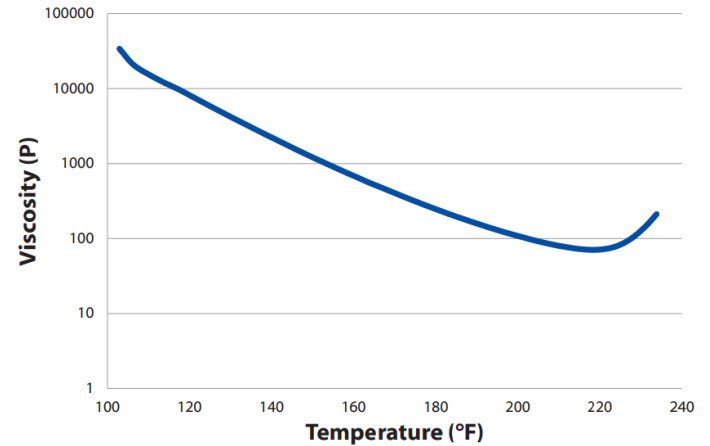

## LAMINA/LAMINATE MECHANICAL PROPERTIES: F6273C-11M (T700S-12K PW)



PROPERTY	SYMBOL	METHOD	UNITS	CTA	RTA	ETW
0° Tensile Strength	$F_{1t}$	ASTM D3039	Ksi (MPa)	145 (1000)	158 (1089)	158 (1089)
90° Tensile Strength	$F_{2t}$	ASTM D3039	Ksi (MPa)	141 (972)	144 (993)	131 (903)
0° Tensile Modulus	$E_{1t}$	ASTM D3039	Msi (GPa)	8.49 (58.5)	8.58 (59.2)	9.12 (62.9)
90° Tensile Modulus	$E_{2t}$	ASTM D3039	Msi (GPa)	8.25 (56.9)	8.23 (56.7)	8.59 (59.2)
0° Compressive Strength	$F_{1c}$	ASTM D6641	Ksi (MPa)	106 (731)	97.7 (674)	74.6 (514)
90° Compressive Strength	$F_{2c}$	ASTM D6641	Ksi (MPa)	104 (717)	92.6 (638)	65.5 (452)
0° Compressive Modulus	$E_{1c}$	ASTM D6641	Msi (GPa)	7.15 (49.3)	7.73 (53.3)	8.4 (57.9)
90° Compressive Modulus	$E_{2c}$	ASTM D6641	Msi (GPa)	7.22 (49.8)	7.04 (48.5)	8.18 (56.4)
In-Plane Shear Strength @ 5%	$F_{12}$	ASTM D5379	Ksi (MPa)	17.2 (119)	12.5 (86.2)	6.92 (47.7)
In-Plane Shear Modulus	$G_{12}$	ASTM D5379	Msi (GPa)	0.695 (4.79)	0.582 (4.01)	0.429 (2.96)
Short Beam Shear Strength	SBS	ASTM D2344	Ksi (MPa)	10.1 (69.6)	9.83 (67.8)	4.63 (31.9)
Poisson's Ratio	$\nu_{12}$	ASTM D3039	-	0.057	0.054	0.024
Open Hole Compression Strength (QI: 25/50/25)	OHC	ASTM D6484	Ksi (MPa)	49.1 (339)	39.5 (272)	30.4 (210)
Compression After Impact @ 1500 in-lb/in (QI: 25/50/25)	CAI	ASTM D7137	Ksi (MPa)	28.3 (195)	25.9 (179)	19.9 (137)
Laminate Density	$\rho$	ASTM D792	g/cc	1.51		
Fiber Volume Fraction	$V_f$	ASTM D3171	%	48.2		
Cured Ply Thickness	CPT	-	Inches (mm)	0.0086 (0.218)		

### Notes:

CTA: -65°F (-54°C), Ambient

RTA: 72°F (22°C), Ambient

ETW: 180°F (82°C), conditioned at 160°F/85% RH until equilibrium

Tension and compression values are normalized to the indicated CPT values

## LAMINA/LAMINATE MECHANICAL PROPERTIES: P711AG-15 (T700G-12K UD)

PROPERTY	SYMBOL	METHOD	UNITS	CTA	RTA	ETW
0° Tensile Strength	$F_{1t}$	ASTM D3039	Ksi (MPa)	272 (1847)	321 (2212)	272 (1874)
0° Tensile Modulus	$E_{1t}$	ASTM D3039	Msi (GPa)	17.8 (123)	17.6 (121)	17.8 (123)
0° Compressive Strength	$F_{1c}$	SACMA SRM 1	Ksi (MPa)	235 (1619)	231 (1592)	166 (1144)
In-Plane Shear Strength @ Ultimate	$F_{12}$	ASTM D3518	Ksi (MPa)	-	25.0 (172)	-
Short Beam Shear Strength	SBS	ASTM D2344	Ksi (MPa)	-	15.4 (106)	-
Open Hole Compression Strength (QI: 25/50/25)	OHC	ASTM D6484	Ksi (MPa)	-	42.8 (295)	34.2 (236)
Compression After Impact (QI: 25/50/25)	CAI	ASTM D7137	Ksi (MPa)	-	26.2 (181)	-
Fiber Volume Fraction	$V_f$	ASTM D3171	%	54.7		
Cured Ply Thickness	CPT	-	Inches (mm)	0.0058 (0.148)		

## LAMINA/LAMINATE MECHANICAL PROPERTIES: P211AS-200 (T800S-24K UD)

PROPERTY	SYMBOL	METHOD	UNITS	RTA	ETW
0° Tensile Strength	$F_{1t}$	ASTM D3039	Ksi (MPa)	405 (2792)	-
90° Tensile Strength	$F_{2t}$	ASTM D3039	Ksi (MPa)	7.4 (51)	2.7 (18.6)
0° Tensile Modulus	$E_{1t}$	ASTM D3039	Msi (GPa)	21.1 (145)	-
90° Tensile Modulus	$E_{2t}$	ASTM D3039	Msi (GPa)	1.3 (9)	-
0° Compressive Strength	$F_{1c}$	ASTM D6641	Ksi (MPa)	180 (1241)	-
90° Compressive Strength	$F_{2c}$	ASTM D6641	Ksi (MPa)	32 (221)	17.6 (121)
0° Compressive Modulus	$E_{1c}$	ASTM D6641	Msi (GPa)	18 (124)	-
90° Compressive Modulus	$E_{2c}$	ASTM D6641	Msi (GPa)	1.3 (9)	1.2 (8.3)
In-Plane Shear Strength @ 5%	$F_{12}$	ASTM D5379	Ksi (MPa)	13.1 (90.3)	7.6 (52.4)
In-Plane Shear Modulus	$G_{12}$	ASTM D5379	Msi (GPa)	0.55 (3.79)	0.49 (3.38)
Short Beam Shear Strength	SBS	ASTM D2344	Ksi (MPa)	13.3 (91.7)	-
Open Hole Compression Strength (QI: 25/50/25)	OHC	ASTM D6484	Ksi (MPa)	43 (296)	33.7 (232)
Laminate Density	$\rho$	ASTM D792	g/cc	1.54	
Fiber Volume Fraction	$V_f$	ASTM D3171	%	54.9	
Cured Ply Thickness	CPT	-	Inches (mm)	0.0079 (0.201)	

**LAMINA/LAMINATE MECHANICAL PROPERTIES: FM6673G-11M (T830H-6K PW)**

PROPERTY	SYMBOL	METHOD	UNITS	RTA	ETW
90° Tensile Strength	$F_{2t}$	ASTM D3039	Ksi (MPa)	123 (848)	-
90° Tensile Modulus	$E_{2t}$	ASTM D3039	Msi (GPa)	9.89 (68.2)	-
90° Compressive Strength	$F_{2c}$	ASTM D6641	Ksi (MPa)	96.1 (6.63)	-
90° Compressive Modulus	$E_{2c}$	ASTM D6641	Msi (GPa)	8.82 (60.8)	-
In-Plane Shear Strength @ 5%	$F_{12}$	ASTM D5379	Ksi (MPa)	16.3 (112)	8.14 (56.1)
In-Plane Shear Modulus	$G_{12}$	ASTM D5379	Msi (GPa)	0.51 (3.52)	0.42 (2.9)
Short Beam Shear Strength	SBS	ASTM D2344	Ksi (MPa)	8.91 (61.4)	-
Open Hole Compression Strength (QI: 25/50/25)	OHC	ASTM D6484	Ksi (MPa)	39.9 (275)	34.8 (240)
Laminate Density	$\rho$	ASTM D792	g/cc	1.54	
Fiber Volume Fraction	$V_f$	ASTM D3171	%	48.6	
Cured Ply Thickness	CPT	-	Inches (mm)	0.0089 (0.226)	

**LAMINA/LAMINATE MECHANICAL PROPERTIES: P6111-200 (M46J UD)**

PROPERTY	SYMBOL	METHOD	UNITS	RTA
0° Tensile Strength	$F_{1t}$	ASTM D3039	Ksi (MPa)	244 (1682)
90° Tensile Strength	$F_{2t}$	ASTM D3039	Ksi (MPa)	7.4 (51)
0° Tensile Modulus	$E_{1t}$	ASTM D3039	Msi (GPa)	32.6 (225)
90° Tensile Modulus	$E_{2t}$	ASTM D3039	Msi (GPa)	1.3 (9)
0° Compressive Strength	$F_{1c}$	ASTM D6641	Ksi (MPa)	120 (827)
90° Compressive Strength	$F_{2c}$	ASTM D6641	Ksi (MPa)	32 (221)
0° Compressive Modulus	$E_{1c}$	ASTM D6641	Msi (GPa)	26.2 (181)
90° Compressive Modulus	$E_{2c}$	ASTM D6641	Msi (GPa)	1.3 (9)
In-Plane Shear Strength @ 5%	$F_{12}$	ASTM D5379	Ksi (MPa)	10 (68.9)
In-Plane Shear Modulus	$G_{12}$	ASTM D5379	Msi (GPa)	0.55 (3.79)
Short Beam Shear Strength	SBS	ASTM D2344	Ksi (MPa)	9.4 (64.8)
Open Hole Compression Strength (QI: 25/50/25)	OHC	ASTM D6484	Ksi (MPa)	31.1 (214)
Laminate Density	$\rho$	ASTM D792	g/cc	1.52
Fiber Volume Fraction	$V_f$	ASTM 3171	%	51
Cured Ply Thickness	CPT	-	Inches (mm)	0.0084 (0.213)

## LAMINA/LAMINATE MECHANICAL PROPERTIES: F4829-11M (M46J-6K PW)

PROPERTY	SYMBOL	METHOD	UNITS	RTA
90° Tensile Strength	$F_{2t}$	ASTM D3039	Ksi (MPa)	83 (572)
90° Tensile Modulus	$E_{2t}$	ASTM D3039	Msi (GPa)	13.8 (95.1)
90° Compressive Strength	$F_{2c}$	ASTM D6641	Ksi (MPa)	70.2 (484)
90° Compressive Modulus	$E_{2c}$	ASTM D6641	Msi (GPa)	12 (82.7)
In-Plane Shear Strength @ 5%	$F_{12}$	ASTM D5379	Ksi (MPa)	9.3 (64.1)
In-Plane Shear Modulus	$G_{12}$	ASTM D5379	Msi (GPa)	0.57 (3.93)
Short Beam Shear Strength	SBS	ASTM D2344	Ksi (MPa)	6.7 (46.2)
Open Hole Compression Strength (25/50/25)	OHC	ASTM D6484	Ksi (MPa)	31.4 (216)
Fiber Volume Fraction	$V_f$	ASTM 3171	%	48.4
Cured Ply Thickness	CPT	-	Inches (mm)	0.0094 (0.239)

### Notes:

CTA: -65°F (-54°C), Ambient

RTA: 72°F (22°C), Ambient


ETW: 180°F (82°C), conditioned at 160°F/85% RH until equilibrium

Tension and compression values are normalized to the indicated CPT values

## LAMINA/LAMINATE MECHANICAL PROPERTIES: FGF108-11M

PROPERTY	SYMBOL	METHOD	UNITS	CTA	RTA	ETW
Cured Ply Thickness	CPT	-	Inches (mm)		0.0016 (0.0406)	

## BAGGING PROCEDURE

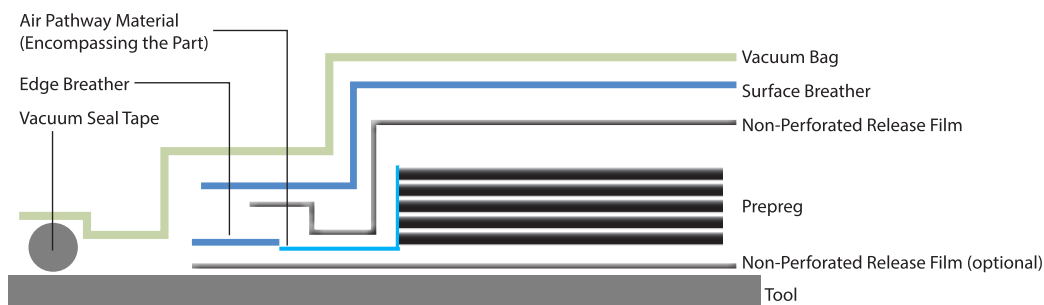

### Notes:

1. Debulk every four plies, or as needed, when laying up material.
2. It is recommended that panels have a pre-cure vacuum hold depending on size: for small panels 1 hour, for medium sized panels (>1ft<sup>2</sup>) for 3 hours, and for complex layouts (ply drops, >2ft<sup>2</sup>) for 16+ hours.
3. The vacuum should be checked for leaks before beginning the cure cycle. The leak rate shall be less than 2.0 inches of Hg (7 kPa) over 5 minutes.


**Please refer to the SDS for handling and disposal.**

The data listed herein are lot averages, for reference purposes only, and are offered AS-IS without warranty. The results are not intended for specification purposes. WARNING: This document may contain technical data whose export is restricted by the Export Administration Act of 1979, as amended, Title 50, U.S.C., App.2401 et seq. Violations of these export laws are subject to severe criminal penalties.

## RECOMMENDED OVEN CURE CYCLE

1. Apply full vacuum\* to the part. Higher vacuum levels will yield better results.
2. Maintaining vacuum for at least three hours prior to beginning cure cycle is recommended for optimal part quality. This promotes the extraction of trapped air and gases, producing a lower void content.
3. Ramp to  $270 \pm 10^{\circ}\text{F}$  at  $1\text{-}5^{\circ}\text{F}/\text{min}$  ( $132 \pm 5^{\circ}\text{C}$  at  $0.6\text{-}2.8^{\circ}\text{C}/\text{min}$ ) and hold for 120 minutes.
4. Cool temperature down to  $130^{\circ}\text{F}$  at max rate of  $5^{\circ}\text{F}/\text{min}$  ( $54^{\circ}\text{C}$  at  $2.8^{\circ}\text{C}/\text{min}$ ).

\* Required vacuum level varies depending on elevation. 28" Hg (95 kPa) is the recommended minimum at sea level under average conditions.

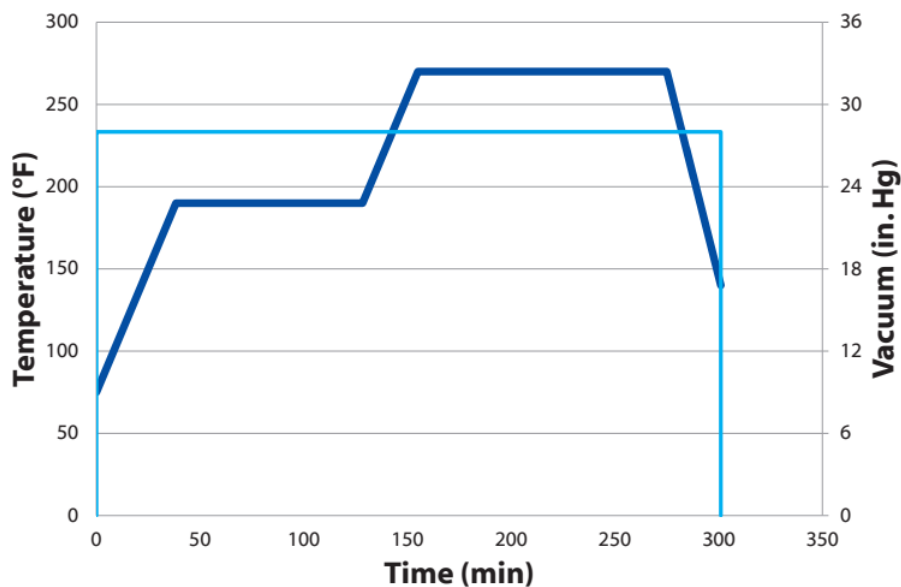

# TORAY

Toray Composite Materials America, Inc.

[www.toraycma.com](http://www.toraycma.com)

[salescmacontact@toraycma.com](mailto:salescmacontact@toraycma.com)

253-846-1777 • 800-208-6729